

AFRL-AFOSR-VA-TR-2016-0243

Inverse Design, Development and Characterization of Catalytic Adsorbates at Semiconductor/Liquid Interfaces

Victor Batista YALE UNIV NEW HAVEN CT 105 WALL ST NEW HAVEN, CT 06511-6614

07/08/2016 Final Report

DISTRIBUTION A: Distribution approved for public release.

Air Force Research Laboratory
AF Office Of Scientific Research (AFOSR)/RTB2

Arlington, Virginia 22203 Air Force Materiel Command

REPORT DOCUMENTATION PAGE

Form Approved OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to the Department of Defense, Executive Service Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no

| person shall be subject to any penalty for failing to co PLEASE DO NOT RETURN YOUR FO | • • | | valid OMB co | ntrol number. | |
|--|--------------------------------------|-------------------|----------------------|--|--|
| 1. REPORT DATE (DD-MM-YYYY) 24-06-2016 | 2. REPORT TYPE Final Rep | ort | | 3. DATES COVERED (From - To) From 01-01-2013 to 30-06-2016 | |
| 4. TITLE AND SUBTITLE | | | 5a. CON | ITRACT NUMBER | |
| Inverse Design, Development and Cha | racterization of Catalytic Adsorbat | es at | | | |
| Semiconductor/Liquid Interfaces | | | <u> </u> | WIT WILLIAM TO THE TOTAL THE TOTAL TO THE TOTAL THE TOTAL TO THE TOTAL THE TOTAL TO THE TOTAL TOTAL TO THE TO | |
| | | | 5b. GRA | ANT NUMBER | |
| | | | | FA9550-13-1-0020 | |
| | | | 5c. PRO | GRAM ELEMENT NUMBER | |
| A 117110P(0) | | | E L DDG | NEOT NUMBER | |
| 6. AUTHOR(S) Victor S Potisto (Vola University) Clif | fford D. Vyhioly (University of | | ou. PRC | DJECT NUMBER | |
| Victor S Batista (Yale University), Clif | | | | | |
| California, San Diego) and Tianquan Lian (Emory University), | | | 5e. TASK NUMBER | | |
| | | | F()4(0F | | |
| | | | 5f. WORK UNIT NUMBER | | |
| 7. PERFORMING ORGANIZATION NA | AME(S) AND ADDRESS(ES) | | | 8. PERFORMING ORGANIZATION | |
| Yale University | (-, | | | REPORT NUMBER | |
| Dept. of Chemistry | | | | | |
| 225 Prospect Street | | | | | |
| New Haven, CT 06511 | | | | | |
| 9. SPONSORING/MONITORING AGE | NCY NAME(S) AND ADDRESS(ES |) | | 10. SPONSOR/MONITOR'S ACRONYM(S) | |
| Dr. Michael Berman, AFOSR/RSA | | | | | |
| 875 N. Randolph Street, Room 3112 | | | | | |
| Arlington, VA 22203-1954 | | | | 11. SPONSOR/MONITOR'S REPORT NUMBER(S) | |
| 12. DISTRIBUTION/AVAILABILITYST/ | ATEMENT | | | | |
| DISTRIBUTION A: Distribution approved for public release. | | | | | |
| | | | | | |
| 13. SUPPLEMENTARY NOTES | | | | | |
| None | | | | | |
| 14. ABSTRACT | | | | | |
| | e University), Kubiak (University of | of California, Sa | n Diego) a | and Lian (Emory University), have made | |
| significant progress in the understanding of the operation of catalysts for CO2 reduction on surfaces, including Re(I) bipyridyl complexes, Ni | | | | | |
| | | | | techniques for studying catalytic reactions | |
| | | | | nical, computational, and spectroscopic | |
| techniques, especially as related to sum frequency generation spectroscopy (SFG) and in situ electrochemical SFG. | | | | | |
| | | | | | |
| | | | | | |
| | | | | | |
| 15. SUBJECT TERMS | | | | | |
| Theoretical mechanistic studies of CO | 2 reduction, sum frequency general | tion (SFG) spect | roscopy o | f catalysts at electrode surfaces, Re(I) bipyridyl | |
| complexes, Ni(cyclam) catalyst, pyridi | | - | | | |
| 46 SECUDITY OF ASSISTANCE | 17. LIMITATION OF | 18 NIIMPED | 10a NAN | IE OF RESPONSIBLE PERSON | |
| 16. SECURITY CLASSIFICATION OF: | ADOTDAOT | OF | Victor 1 | | |

U

PAGES

13

b. ABSTRACT | c. THIS PAGE

U

U

a. REPORT

U

19b. TELEPHONE NUMBER (Include area code)

203-432-6672

Victor Batista

INSTRUCTIONS FOR COMPLETING SF 298

- **1. REPORT DATE.** Full publication date, including day, month, if available. Must cite at least the year and be Year 2000 compliant, e.g. 30-06-1998; xx-vx-1998.
- **2. REPORT TYPE.** State the type of report, such as final, technical, interim, memorandum, master's thesis, progress, quarterly, research, special, group study, etc.
- **3. DATES COVERED.** Indicate the time during which the work was performed and the report was written, e.g., Jun 1997 Jun 1998; 1-10 Jun 1996; May Nov 1998; Nov 1998.
- **4. TITLE.** Enter title and subtitle with volume number and part number, if applicable. On classified documents, enter the title classification in parentheses.
- **5a. CONTRACT NUMBER.** Enter all contract numbers as they appear in the report, e.g. F33615-86-C-5169.
- **5b. GRANT NUMBER.** Enter all grant numbers as they appear in the report, e.g. AFOSR-82-1234.
- **5c. PROGRAM ELEMENT NUMBER.** Enter all program element numbers as they appear in the report, e.g. 61101A.
- **5d. PROJECT NUMBER.** Enter all project numbers as they appear in the report, e.g. 1F665702D1257; ILIR.
- **5e. TASK NUMBER.** Enter all task numbers as they appear in the report, e.g. 05; RF0330201; T4112.
- **5f. WORK UNIT NUMBER.** Enter all work unit numbers as they appear in the report, e.g. 001; AFAPL30480105.
- **6. AUTHOR(S).** Enter name(s) of person(s) responsible for writing the report, performing the research, or credited with the content of the report. The form of entry is the last name, first name, middle initial, and additional qualifiers separated by commas, e.g. Smith, Richard, J, Jr.
- 7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES). Self-explanatory.

8. PERFORMING ORGANIZATION REPORT NUMBER.

Enter all unique alphanumeric report numbers assigned by the performing organization, e.g. BRL-1234; AFWL-TR-85-4017-Vol-21-PT-2.

- 9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES). Enter the name and address of the organization(s) financially responsible for and monitoring the work.
- **10. SPONSOR/MONITOR'S ACRONYM(S).** Enter, if available, e.g. BRL, ARDEC, NADC.
- **11. SPONSOR/MONITOR'S REPORT NUMBER(S).** Enter report number as assigned by the sponsoring/monitoring agency, if available, e.g. BRL-TR-829; -215.
- **12. DISTRIBUTION/AVAILABILITY STATEMENT.** Use agency-mandated availability statements to indicate the public availability or distribution limitations of the report. If additional limitations/ restrictions or special markings are indicated, follow agency authorization procedures, e.g. RD/FRD, PROPIN, ITAR, etc. Include copyright information.
- **13. SUPPLEMENTARY NOTES.** Enter information not included elsewhere such as: prepared in cooperation with; translation of; report supersedes; old edition number, etc.
- **14. ABSTRACT.** A brief (approximately 200 words) factual summary of the most significant information.
- **15. SUBJECT TERMS.** Key words or phrases identifying major concepts in the report.
- **16. SECURITY CLASSIFICATION.** Enter security classification in accordance with security classification regulations, e.g. U, C, S, etc. If this form contains classified information, stamp classification level on the top and bottom of this page.
- 17. LIMITATION OF ABSTRACT. This block must be completed to assign a distribution limitation to the abstract. Enter UU (Unclassified Unlimited) or SAR (Same as Report). An entry in this block is necessary if the abstract is to be limited.

2016 AFOSR Final Report

Victor S. Batista, Clifford P. Kubiak and Tianquan Lian

Research progress.

We, the collaborative team of Batista (Yale University), Kubiak (University of California, San Diego) and Lian (Emory University), have made significant progress in the understanding of the operation of catalysts for CO₂ reduction on surfaces, including Re(I) bipyridyl complexes, Ni(cyclam) complexes, and pyridine-based molecules as well as development of *in situ* spectroscopic techniques for studying catalytic reactions during the last grant period. Each project involves an intimate combination of synthetic, electrochemical, computational, and spectroscopic techniques, especially as related to sum frequency generation spectroscopy (SFG) and *in situ* electrochemical SFG.

1. Coupled experimental and theoretical determination of orientation of Re(I) bipyridyl complexes for CO₂ reduction on Au and on TiO₂.

We have recently determined the binding orientations of Re(I) bipyridyl complexes with different anchoring groups on two different surfaces. First, we used sum frequency generation spectroscopy and calculations of SFG spectra, based on density functional theory, to investigate Re(R-2,2'-bipyridine)(CO)₃Cl (R = 4-cyano or 4,4'-dicyano) electrocatalysts binding to gold electrodes. Understanding the orientation of these complexes is critical for redox state transitions and catalytic turnover.

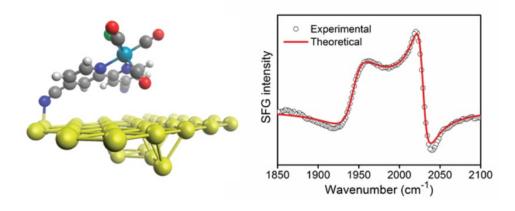


Figure 1. *Left.* DFT optimized monodentate geometry for the dicyano Re complex with its axial CO facing the surface with a tilt angle of 63° relative to the surface normal. *Right.* Representative PPP-polarized SFG spectra of monolayers of the dicyano Re

complex adsorbed onto gold thin films (black circles) with DFT simulations of the SFG spectra using the geometry on the left (red).

We found that the electrocatalysts lean on the Au surface and orient the plane of the bipyridine ligand at 63° relative to the surface normal by computing several binding geometries in DFT and determine which gives orientations and thus SFG spectra that best match the experimentally measured spectra. These findings, recently published in the Journal of Physical Chemistry C (Clark 2016), demonstrate the capabilities of the approach including rigorous spectroscopic and theoretical methods for revealing the conformation and orientation of CO₂ reduction catalysts bound to electrode surfaces. This information has consequences for catalytic turnover, as the labile chloride ligand and therefore reactive site of the metal is oriented away from the surface, thus no crowding will occur. Current efforts are focused on exploring alternative anchoring groups including thiol, phosphonate, and isocyanide as well as other substrate surfaces including Si.

Our other effort, recently published in the Journal of Physical Chemistry C (Ge 2016), was focused on surface-induced anisotropic binding of the same catalyst, but with carboxyl anchoring groups (ReCOA) on rutile single-crystalline TiO₂ (110) surfaces relative to (001) surfaces using vibrational sum frequency generation (SFG) spectroscopy. The SFG signal shows an isotropic distribution with the rotation of the TiO₂ (001) surface relative to the incident plane, but an anisotropic distribution with the rotation of the TiO₂ (110) surface (Figure 2, top). By combining these results with ab initio SFG simulations and with modeling of ReC0A-TiO₂ cluster binding structures at the density functional theory level, we revealed that the origin of the optical anisotropy for ReC0A on the TiO₂ (110) surface is associated with the binding preference of ReC0A along the [-110] axis. Along this direction, the binding structure is energetically favorable due to the formation of proper hydrogen bonding between the carboxylate group and passivating water molecules on the TiO₂ (110) surface (Figure 2, bottom). The tilt angle, defined by the bipyridyl ring angle relative to the surface normal, of the catalyst is found to be a combination of 26° and 18°, which corresponds to an aggregate at high surface coverage with minimal steric interactions. Since molecular orientation in these systems can significantly influence their catalytic performance, the ability to control the molecular ordering through careful selection of the surface structure and symmetry would be

extremely beneficial. This investigation of catalytic molecules on surfaces with different symmetries helps to elucidate how the degree of molecular ordering depends on surface structure and therefore is of great practical interest, which will inform our selection of substrates in future work.

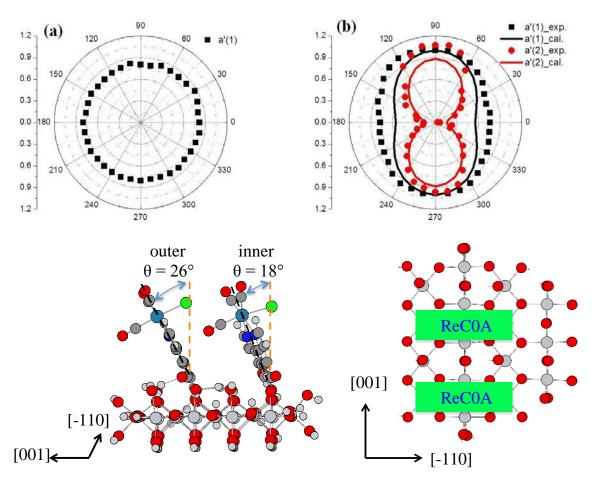


Figure 2. *Top*. Polar plots of the azimuthal dependence of the amplitude for (a) the a'(1) mode of ReC0A on TiO₂ (001) and (b) a'(1) and a'(2) modes of ReC0A on TiO₂ (110). Black squares (a'(1)) and red circles (a'(2)) are experimental results; Solid lines are theoretical results. The amplitude of the a'(1) mode at $\phi = 90^{\circ}$ for ReC0A/TiO₂ (110) system is normalized to one with all other data points for each mode scaled accordingly. *Bottom.* Binding structures of two ReC0A complexes as a dimer on the TiO₂ (110) surface along the [-110] axis from the side (left) and from above, with the ReC0A complexes represented by green rectangles indicating the binding sites (right). Hydrogen bonding to the ReC0A complexes is depicted using dashed bonds. The atoms are colored as follows: with green = Cl, silver = Ti, cerulean = Re, white = H, red = O, gray = C, and blue = N. The tilt angles of each catalyst are indicated by the angle formed by the bpy ring (black dotted line) and the surface normal (orange dotted line). The black arrows indicate the crystal directions on the surface for each panel.

2. The surface as a ligand: the electronic origins of catalytic enhancement of Ni(cyclam) activity by amalgated gold electrodes (Au/Hg).

Ni(cyclam) has been the focus of many investigations as a CO₂ reduction catalyst, but it suffers from poisoning from CO. However, a dramatic enhancement of electrochemical CO₂ conversion to CO, catalyzed by [Ni(cyclam)](PF₆)₂, is observed on Au/Hg electrodes when compared to other metallic electrodes such as Zn. Thus, our recent efforts, in an article being prepared for submission, have focused on understanding the underlying reaction mechanism responsible for the increase in turnover frequency using DFT calculations on cluster models with or without CO bound. The computed trans-III conformer structures on the Au/Hg and Zn electrodes are given in Figure 3 where similar effects are found between conformers. We found that that Hg provides favorable interactions for enhanced reaction kinetics by stabilizing the CO unbound form of the catalyst, predominantly with the *trans*-III conformation, due to reduced Ni-CO reverse dative interactions when compared to the complex in solution, or bound to other metallic surfaces. The higher CO stretching frequency, shorter CO bond, longer Ni-C(O) bond, more linear Ni-C-O angle, and spin-density closer to the formal oxidation number of Ni(I) correlate with lower CO desorption free energies. These findings are particularly relevant to the design of electrode surfaces for activation of electrocatalytic transition metal complexes with common surface interactions that could improve catalyst performance under cell operating conditions.

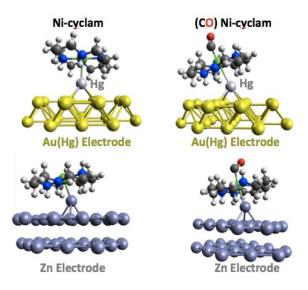


Figure 3. DFT optimized configurations of [Ni(cyclam)]⁺ on Au/Hg (top) and Zn (bottom), without CO (left) and CO bound (right). Color key: yellow: Au, silver: Hg, blue: N, white: H, green: Ni, red: O, dark gray: carbon, purple: Zn.

3. Proton-coupled electron transfer (PCET) in the reduction of 4,4'-bipyridine with CdSe quantum dots and in the reduction of pyridinium on platinum for the conversion of CO_2 to methanol.

Our efforts into the understanding of PCET in pyridine-based molecules are based on two fronts: reduction of bipyridine by CdSe quantum dots and of pyridinium by Pt electrodes. In the first case, recently published in the Journal of the American Chemical Society (Chen 2016), we studied the photo-reduction of 4,4'-bipyridium (bPYD) using CdSe quantum dots (QDs) as a model system for interfacial PCET. We observed ultrafast photo-induced PCET from CdSe QDs to form doubly protonated [bPYDH2]^{+**} radical cations at low pH (4-6). Through studies of the dependence of PCET rates on isotope substitution, pH and bPYD concentration, the radical formation mechanism was identified to be a sequential interfacial electron and proton transfer (ET/PT) process (Figure 4a) with a rate limiting pH independent electron transfer rate constant, k_{int} , of $1.05 \pm 0.13 \times 10^{10} \text{ s}^{-1}$ between a QD and an adsorbed singly protonated [bPYDH]⁺. In the presence of sacrificial electron donors, this system was shown to be capable of generating [bPYDH2]^{+**} radical cations under continuous illumination at 405 nm with a steady-state photoreduction quantum yield of $1.1 \pm 0.1\%$ at pH 4. DFT geometry optimizations of

4,4'-bipyridine on a model CdSe cluster were carried out in the presence of bound 3mercaptopropionic acid (MPA) and were compared to equivalent calculations of methylviologen. The binding geometry is given in Figures 4b and 4c. The optimized structure for bPYD shows asymmetrical hydrogen bonding so that only one H⁺ is bonded to the bPYD (1.22 Å) while the other H⁺ is merely hydrogen bonding to it (1.59 Å), corroborating the role of [bPYDH]⁺ in electron injection. The hydrogen bonding interaction with the MPA prevents bPYD from getting close to the surface, as opposed to methylviologen with its permanent positive charge, suggesting that the faster injection into methylviologen is due to its ability to bind closer to the surface. Theoretical studies of the adsorption of [bPYDH]⁺ and methylviologen on QD surfaces revealed important effects of hydrogen bonding with the capping ligand (3-mercaptopropionic acid) on binding geometry and interfacial PCET. The mechanism of bPYD photo-reduction reported in this work may provide useful insights into the catalytic roles of pyridine and pyridine derivatives in the electrochemical and photoelectrochemical reduction of CO₂. This work established that QDs can be used as a model system for studying interfacial PCET mechanisms.

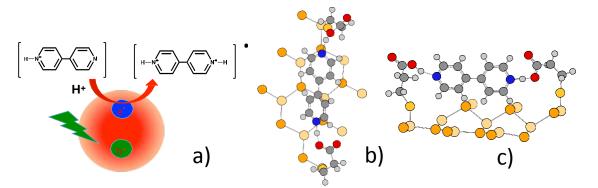


Figure 4. Interfacial proton-coupled electron transfer from QDs. a) Scheme of proton-coupled electron transfer from QDs to bipyridine. b) and c) Structure of bPYD on the CdSe $\{100\}$ cluster model from above (panel b) and from the side (panel c). The color code is as follows: white = H, red = O, gray = C, yellow = S, blue = N, brown = Se, and tan = Cd.

(i)
$$HN \longrightarrow NH^+ + H_2O \longrightarrow HN \longrightarrow N + H_3O^+$$

(ii) $HN \longrightarrow NH^+ + Pt \longrightarrow HN \longrightarrow N + Pt \longrightarrow H$
(iii) $HN \longrightarrow NH^+ + O=C=O + H-Pt \longrightarrow HN \longrightarrow N + HCOOH + Pt$
 $O=C=O + 2HN \longrightarrow NH^+ \longrightarrow Pt \longrightarrow HCOOH + 2HN \longrightarrow N$
 $ImH^+(ad) + Pt(s) + e^- \longrightarrow Pt \longrightarrow Pt-H(s) + Im(aq)$
(ii.1) $\downarrow 6.5 \text{ kcal/mol}$
 $ImH^+(aq) + Pt(s) + e^- \longrightarrow 1/2H_2(g) + Pt(s) + Im(aq)$

Figure 5. *Top:* proposed mechanism of electrochemical reduction of CO_2 on Pt (111) in an aqueous imidazole solution (pH = 5.2). *Bottom:* Thermodynamic cycle (ii.1)–(ii.3) used to obtain the free energy change due to reduction of imidazolium adsorbed to the Pt surface to form Pt-hydride on the surface.

In the second case, as published recently in collaboration with Bocarsly and coworkers in Topics in Catalysis (Liao 2015), we have computationally found that the mechanism of CO₂ reduction by imidazolium is similar to the reduction by pyridinum, as given in Figure 5, top. It was found to form H adsorbates on the electrode surface through a one-electron PCET reaction (-0.68 V vs. SCE as computed by Figure 5, bottom) rather than a one-electron reduction to the imidazolium radical. The cycle includes surface desorption of imidazolium to dihydrogen and imidazole in the aqueous solution (ii.2), and dissociative desorption of H to the Pt surface (ii.3). The reduction potential of imidazolium to H and imidazole (ii.2) was predicted to be -0.60 V, in good agreement with the reduction potential observed by CV experiments, while the free energy changes for reactions (ii.1) and (ii.3) approximately cancel each other. These results are particularly valuable since they suggest that H adsorbates, as recently corroborated through our other recent collaborative work with isotope effects on electrochemistry, published in the Journal of the Electrochemistry Society (Zeitler 2015), could be

generated at low overpotentials by either of the two electrocatalysts. The H adsorbates might react as Pt-hydrides and reduce CO₂ through a proton coupled hydride transfer (PCHT) mechanism, as recently proposed for the electrocatalytic reduction of CO₂ to formic acid in the presence of pyridinium where the electrophilic attack of CO₂ onto the surface hydride is activated by the Brønsted acid in solution.

4. Vibrational relaxation dynamics of $Re(R-2,2'-bipyridine)(CO)_3Cl$ (R=4,4'-dicyano) electrocatalyst.

We have started to investigate how metal electrodes and interfacial solvent environment affect vibrational energy relaxation dynamics of catalysts, a process that is intimately coupled to chemical reactions. We have studied vibrational relaxation dynamics of Re(R-2,2'-bipyridine)(CO)₃Cl (R = 4,4'-dicyano) electrocatalyst on gold and TiO₂ surfaces and in different solvents. Vibrational dynamics of Re complex monolayer bound to the gold surface was probed by IR pump/SFG probe spectroscopy (Figure 6a). Vibrational relaxation dynamics of Re complexes adsorbed on nanoporous TiO₂ thin film and in solution were measured by IR pump/IR probe transient absorption spectroscopy. Our initial results showed that the both metal electrodes and solvent facilitates the vibrational relaxation of CO stretching modes in the Re complex (Figure 6b). Ongoing theoretical calculations are aimed at revealing the mechanisms by which the substrate and solvent affect the vibrational relaxation of Re(I) electrocatalysts using anharmonic coupling constants as yielded by electronic structure calculations.

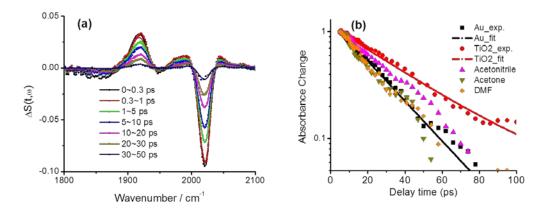


Figure 6. a) Normalized time resolved-SFG difference spectra of three CO stretching modes of Re(I) electrocatalyst on Au at indicated averaged delay times. Solid circles represent experimental data; solid lines represent fits. b) Kinetics of the GSB of in-phase symmetric stretch mode for Re(I) electrocatalyst on Au, TiO₂, and in different solvents. Symbols represent experimental data; lines represent fits.

5. *In situ* electrochemical SFG: electric field effects at the electrode.

Our latest effort involves investigating the electrochemical Stark effect via SFG spectroscopy in order to correlate dependence of vibrational frequencies of chemisorbates on the electrode potential to useful information about the double-layer structure at the electrode/solution interface. We are investigating the Stark effect from the nitrile/isocyanide-terminated self-assembled monolayers (SAMs) on the gold electrode surface. A series of molecules with different terminal groups, symmetry, or length was chosen to systematically study the local electrical fields near the electrode surface. To further understand the Stark effect on the SAMs systems, theoretical calculations were performed to simulate the vibrational frequency shift of nitrile or isocyanide groups in response to local electrical fields. For example, Fig. 7a shows a scheme of 1,4-phenylene diisocyanide (PDI) adsorbed on the electrode surface. Fig. 7b shows the potentialdependent SFG signals of isocyanide groups. At 0 V vs. Ag/AgCl, two peaks around 2120 (free -NC) and 2170 cm⁻¹ (Au bonded -NC) were observed. At more negative potentials, a blue shift of the free N=C mode and a red shift of the Au bonded N=C mode were observed (Fig. 7c). Such a difference could be explained by the different responses to the electric fields for these two groups, which have opposite dipoles (Fig. 7d).

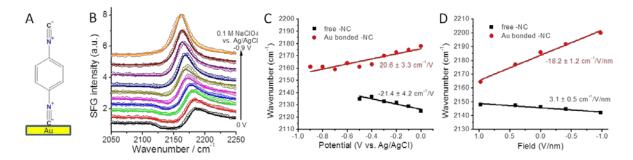


Figure 7. (a) Scheme of PDI adsorbed on gold electrode surface. (b) Potential-dependent SFG spectra of the PDI SAM. Circles represent experimental data, solid lines represent fitting results. (c) Experimental peak positions of free -NC and Au bonded -NC under different potentials. (d) Calculated peak positions of free -NC and Au bonded -NC under different electric fields.

Publications with Acknowledgments to the AFOSR:

- Vibrational Relaxation Dynamics of Catalysts on TiO₂ Rutile (110) Single Crystal Surfaces and Anatase Nanoporous Thin Films. Allen M. Ricks, Chantelle L. Anfuso, William Rodríguez-Córdoba, and Tianquan Lian. *Chem. Phys.* 422: 264-271 (2013).
- 2. Functional Role of Pyridinium During Aqueous Electrochemical Reduction of CO₂ on Pt(111), Mehmed Z. Ertem, Steven J. Konezny, C. Moyses Araujo, and Victor S. Batista. *J. Phys. Chem. Lett.* **4**: 745-748 (2013)
- Electrochemical Reduction of Aqueous Imidazolium on Pt (111) by Proton Coupled Electron Transfer. Kuo Liao, Mikhail Askerka, Elizabeth L. Zeitler, Andrew B. Bocarsly, and Victor S. Batista. *Top. Catal.* 58: 23-29 (2015).
- 4. Isotopic Probe Illuminates the Role of the Electrode Surface in Proton Coupled Electron Transfer Electrochemical Reduction of Pyridinium on Pt(111). Elizabeth L. Zeitler, Mehmed Z. Ertem, James Pander, Yong Yan, Victor S. Batista, and Andrew B. Bocarsly. *J. Electrochem. Soc.* 162: H938-H944 (2015)

- 5. Short-Range Catalyst–Surface Interactions Revealed by Heterodyne Two-Dimensional Sum Frequency Generation Spectroscopy. Jiaxi Wang, Melissa L. Clark, Yingmin Li, Camille L. Kaslan, Clifford P. Kubiak, and Wei Xiong. *J. Phys. Chem. Lett.* **6**: 4204-4209 (2015)
- 6. Orientation of Cyano-Substituted Bipyridine Re(I) *fac*-Tricarbonyl Electrocatalysts Bound to Au Electrodes, Melissa L. Clark, Benjamin Rudshteyn, Aimin Ge, Steven A. Chabolla, Charles W. Machan, Brian T. Psciuk, Jia Song, Gabriele Canzi, Tianquan Lian, Victor S. Batista, and Clifford P. Kubiak. *J. Phys. Chem. C* **120**: 1657-1665 (2016).
- 7. Surface-Induced Anisotropic Binding of a Rhenium CO₂-Reduction Catalyst on Rutile TiO₂ (110), Aimin Ge, Benjamin Rudshteyn, Brian T. Psciuk, Dequan Xiao, Jia Song, Chantelle L. Anfuso, Allen M. Ricks, Victor S. Batista, and Tianquan Lian. *J. Phys. Chem C.* In Press (2016).
- 8. Ultrafast Photo-Induced Interfacial Proton Coupled Electron Transfer from CdSe Quantum Dots to 4,4'-Bipyridine. Jinquan Chen, Kaifeng Wu, Benjamin Rudshteyn, Yanyan Jia, Wendu Ding, Zhao-Xiong Xie, Victor S. Batista, and Tianquan Lian. *J. Am. Chem. Soc.* **116**: 26377-26384 (2016).
- Characterizing Interstate Vibrational Coherent Dynamics of Surface Adsorbed Catalysts by Fourth-Order 3D SFG Spectroscopy, Yingmin Li, Jiaxi Wang, Melissa L. Clark, Clifford P. Kubiak and Wei Xiong. *Chem. Phys. Lett.* 650: 1-6 (2016).
- 10. Yanyan Jia, Jinquan Chen, Kaifeng Wu, Alex Kaledin, Djamaladdin G. Musaev, Zhao-Xiong Xie, and Tianquan Lian. Enhancing Photo-Reduction Quantum Efficiency Using Quasi-Type II Core/Shell Quantum Dots. *Chem. Sci.* 7, 4125-4133 (2016).

- 11. Mikhail Askerka, Reinhard J. Maurer, Victor S. Batista, and John C. Tully. Role of Tensorial Electronic Friction in Energy Transfer at Metal Surfaces. *Phys. Rev. Lett.* **116**, 217601 (2016).
- 12. Benjamin Rudshteyn, Hunter B. Vibbert, Richard May, Eric Wasserman, Ingolf Warnke, Michael D. Hopkins, and Victor S. Batista. Regulation of the Redox Properties of Tungsten-Alkylidyne Complexes by Ligand Design. *Inorg. Chem.* Submitted. (2016).
- 13. Prasad S. Lakkaraju, Mikhail Askerka, Heidie Beyer, Charles T. Ryan, Tabbetha Dobbins, Christopher Bennett, Jerry J. Kaczur, and Victor S. Batista. Formate to Oxalate: A Crucial Step for Conversion of CO₂ into Multi-Carbon Compounds. *ChemCatChem.* Under Revision. (2016).
- 14. Benjamin Rudshteyn, Yueshen Wu, Jesse D. Froehlich, Almagul Zhanaidarova, Wendu Ding, Clifford P. Kubiak, and Victor S. Batista. Diminished Reverse Dative Effect Induced by Electrode Surface Enhances Catalytic Activity of the Ni(cyclam) Complex During Electrochemical CO₂ Reduction. *Manuscript in preparation*. (2016).
- 15. Aimin Ge, Jingyi Zhu, Benjamin Rudshteyn, Melissa L. Clark, Mikhail Askerka, Kenneth Jung, Clifford P. Kubiak, Victor S. Batista, and Tianquan Lian. Vibrational Relaxation Dynamics of Rhenium Bipyridyl CO₂-Reduction Catalyst Monolayer on Gold. *Manuscript in preparation*. (2016).
- 16. Aimin Ge, Benjamin Rudshteyn, Gwendolynne L. Merlen, Melissa L. Clark, Jia Song, Clifford P. Kubiak, Victor S. Batista, and Tianquan Lian. Probing Electric Fields at the Nitrile/Isocyanide-Terminated SAMs/Electrode/Liquid Interface by Vibrational SFG Spectroscopy. *Manuscript in preparation*. (2016).

17. Pranammaya Dey, Benjamin Rudshteyn, Mikhail Askerka, Wendu Ding, Victor S. Batista. The Electronic Structure of an Intermediate in a Carbon Dioxide Reduction Reaction as Determined by Computational SFG Spectroscopy. *Manuscript in preparation*. (2016).

1.

1. Report Type

Final Report

Primary Contact E-mail

Contact email if there is a problem with the report.

victor.batista@yale.edu

Primary Contact Phone Number

Contact phone number if there is a problem with the report

2032437880

Organization / Institution name

Yale University

Grant/Contract Title

The full title of the funded effort.

Inverse Design, Development and Characterization of Catalytic Adsorbates

Grant/Contract Number

AFOSR assigned control number. It must begin with "FA9550" or "F49620" or "FA2386".

FA9550-13-1-0020

Principal Investigator Name

The full name of the principal investigator on the grant or contract.

Victor S. Batista

Program Manager

The AFOSR Program Manager currently assigned to the award

Michael R. Berman

Reporting Period Start Date

01/01/2013

Reporting Period End Date

06/30/2016

Abstract

The collaborative team of Batista (Yale University), Kubiak (University of California, San Diego) and Lian (Emory University), have made significant progress in the understanding of the operation of catalysts for CO2 reduction on surfaces, including Re(I) bipyridyl complexes, Ni(cyclam) complexes, and pyridine-based molecules as well as development of in situ spectroscopic techniques for studying catalytic reactions during the last grant period. Each project involves an intimate combination of synthetic, electrochemical, computational, and spectroscopic techniques, especially as related to sum frequency generation spectroscopy (SFG) and in situ electrochemical SFG.

Distribution Statement

This is block 12 on the SF298 form.

Distribution A - Approved for Public Release

Explanation for Distribution Statement

If this is not approved for public release, please provide a short explanation. E.g., contains proprietary information.

SF298 Form

Please attach your SF298 form. A blank SF298 can be found here. Please do not password protect or secure the PDF The maximum file size for an SF298 is 50MB.

DISTRIBUTION A: Distribution approved for public release.

AFD-070820-035 (002).pdf

Upload the Report Document. File must be a PDF. Please do not password protect or secure the PDF. The maximum file size for the Report Document is 50MB.

Finalreport_Yale_Emory_UCSanDiego.pdf

Upload a Report Document, if any. The maximum file size for the Report Document is 50MB.

Archival Publications (published) during reporting period:

- 1. Vibrational Relaxation Dynamics of Catalysts on TiO2 Rutile (110) Single Crystal Surfaces and Anatase Nanoporous Thin Films. Allen M. Ricks, Chantelle L. Anfuso, William Rodríguez-Córdoba, and Tianquan Lian. Chem. Phys. 422: 264-271 (2013).
- 2. Functional Role of Pyridinium During Aqueous Electrochemical Reduction of CO2 on Pt(111), Mehmed Z. Ertem, Steven J. Konezny, C. Moyses Araujo, and Victor S. Batista. J. Phys. Chem. Lett. 4: 745-748 (2013).
- 3. Electrochemical Reduction of Aqueous Imidazolium on Pt (111) by Proton Coupled Electron Transfer. Kuo Liao, Mikhail Askerka, Elizabeth L. Zeitler, Andrew B. Bocarsly, and Victor S. Batista. Top. Catal. 58: 23-29 (2015).
- 4. Isotopic Probe Illuminates the Role of the Electrode Surface in Proton Coupled Electron Transfer Electrochemical Reduction of Pyridinium on Pt(111). Elizabeth L. Zeitler, Mehmed Z. Ertem, James Pander, Yong Yan, Victor S. Batista, and Andrew B. Bocarsly. J. Electrochem. Soc. 162: H938-H944 (2015).
- 5. Short-Range Catalyst–Surface Interactions Revealed by Heterodyne Two-Dimensional Sum Frequency Generation Spectroscopy. Jiaxi Wang, Melissa L. Clark, Yingmin Li, Camille L. Kaslan, Clifford P. Kubiak, and Wei Xiong. J. Phys. Chem. Lett. 6: 4204-4209 (2015).
- 6. Orientation of Cyano-Substituted Bipyridine Re(I) fac-Tricarbonyl Electrocatalysts Bound to Au Electrodes, Melissa L. Clark, Benjamin Rudshteyn, Aimin Ge, Steven A. Chabolla, Charles W. Machan, Brian T. Psciuk, Jia Song, Gabriele Canzi, Tianquan Lian, Victor S. Batista, and Clifford P. Kubiak. J. Phys. Chem. C 120: 1657-1665 (2016).
- 7. Surface-Induced Anisotropic Binding of a Rhenium CO2-Reduction Catalyst on Rutile TiO2 (110), Aimin Ge, Benjamin Rudshteyn, Brian T. Psciuk, Dequan Xiao, Jia Song, Chantelle L. Anfuso, Allen M. Ricks, Victor S. Batista, and Tianguan Lian. J. Phys. Chem C. In Press (2016).
- 8. Ultrafast Photo-Induced Interfacial Proton Coupled Electron Transfer from CdSe Quantum Dots to 4,4'-Bipyridine. Jinquan Chen, Kaifeng Wu, Benjamin Rudshteyn, Yanyan Jia, Wendu Ding, Zhao-Xiong Xie, Victor S. Batista, and Tianquan Lian. J. Am. Chem. Soc. 116: 26377-26384 (2016).
- 9. Characterizing Interstate Vibrational Coherent Dynamics of Surface Adsorbed Catalysts by Fourth-Order 3D SFG Spectroscopy, Yingmin Li, Jiaxi Wang, Melissa L. Clark, Clifford P. Kubiak and Wei Xiong. Chem. Phys. Lett. 650: 1-6 (2016).
- 10. Yanyan Jia, Jinquan Chen, Kaifeng Wu, Alex Kaledin, Djamaladdin G. Musaev, Zhao-Xiong Xie, and Tianquan Lian. Enhancing Photo-Reduction Quantum Efficiency Using Quasi-Type II Core/Shell Quantum Dots. Chem. Sci., 7, 4125-4133 (2016).
- 11. Mikhail Askerka, Reinhard J. Maurer, Victor S. Batista, and John C. Tully. Role of Tensorial Electronic Friction in Energy Transfer at Metal Surfaces. Phys. Rev. Lett. 116, 217601 (2016).
- 2. New discoveries, inventions, or patent disclosures:

 DISTRIBUTION A: Distribution approved for public release.

Do you have any discoveries, inventions, or patent disclosures to report for this period?

No

Please describe and include any notable dates

Do you plan to pursue a claim for personal or organizational intellectual property?

Changes in research objectives (if any):

None

Change in AFOSR Program Manager, if any:

None

Extensions granted or milestones slipped, if any:

Extension from 01-01-2016 to 30-06-2016.

AFOSR LRIR Number

LRIR Title

Reporting Period

Laboratory Task Manager

Program Officer

Research Objectives

Technical Summary

Funding Summary by Cost Category (by FY, \$K)

| | Starting FY | FY+1 | FY+2 |
|----------------------|-------------|------|------|
| Salary | | | |
| Equipment/Facilities | | | |
| Supplies | | | |
| Total | | | |

Report Document

Report Document - Text Analysis

Report Document - Text Analysis

Appendix Documents

2. Thank You

E-mail user

Jun 27, 2016 17:37:16 Success: Email Sent to: victor.batista@yale.edu